


Crystal structure of potassium antimony hexathiodiphosphate, KSbP_2S_6

V. Manriquez^{*,I}, A. Galdámez^I, D. Ruiz León^I and M. T. Garland^{II}

^I Universidad de Chile, Facultad de Ciencias, Departamento de Química, Casilla 653, Santiago, Chile

^{II} Universidad de Chile, Facultad de Ciencias Físicas y Matemáticas, Departamento de Física, Casilla 487-3, Santiago, Chile

Received November 18, 2003, accepted and available on-line November 21, 2003, CSD-No. 409751

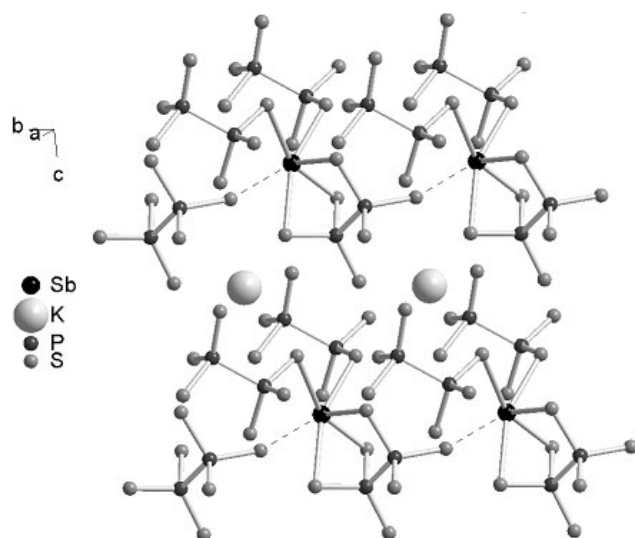

Abstract

KSbP_2S_6 , monoclinic, $P12_11$ (No. 4), $a = 6.605(1) \text{ \AA}$, $b = 7.651(2) \text{ \AA}$, $c = 9.754(2) \text{ \AA}$, $\beta = 92.11(3)^\circ$, $V = 492.6 \text{ \AA}^3$, $Z = 2$, $R_{\text{gt}}(F) = 0.018$, $wR_{\text{ref}}(F^2) = 0.044$, $T = 293 \text{ K}$.

Source of material

For the synthesis of KSbP_2S_6 , the corresponding high purity element powders (99.99%) supplied by Aldrich were mixed in the stoichiometric amounts, sealed in evacuated quartz tubes, and heated at 1023 K for two weeks. After the reaction was completed, the sample was slowly cooled to room temperature. All manipulations were carried out under Ar atmosphere

Discussion

In the course of our work on chalcogen phosphates [1,2], we have prepared the quaternary antimony hexathiodiphosphate KSbP_2S_6 . This compound is isostructural to KBiP_2S_6 [3]. As expected, the Sb—S bonds in KSbP_2S_6 are shorter than the Bi—S bonds in KBiP_2S_6 . Also, the smaller radius of Sb^{3+} results in a decreased coordination number. Thus, each Sb^{3+} is coordinated by five S atoms compared with the six-coordinated Bi^{3+} ions in the isostructural compound. In the title compound, each Sb^{3+} ion is tri-coordinated by one ethane-like $[\text{P}_2\text{S}_6]^{4-}$ ligand and mono-coordinated by two $[\text{P}_2\text{S}_6]^{4-}$ groups forming chains, while a sixth S atom connects the Sb^{3+} to a neighboring chain, through a Sb—S contact of $3.4187(9) \text{ \AA}$, to form a layer in the bc plane. The layers are separated by the K^+ ions. The bond lengths $d(\text{Sb—S})$ range from $2.545(1) \text{ \AA}$ to $3.1471(5) \text{ \AA}$. The compounds KMP_2S_6 ($M = \text{Sb, Bi}$) are structurally related to $\text{Na}_{0.16}\text{Bi}_{1.28}\text{P}_2\text{S}_6$ [4] and $\beta\text{-KMP}_2\text{Se}_6$ [5].

Table 1. Data collection and handling.

Crystal:	yellow block, size $0.089 \times 0.104 \times 0.224 \text{ mm}$
Wavelength:	Mo K_{α} radiation (0.71073 \AA)
μ :	47.43 cm^{-1}
Diffractometer, scan mode:	Bruker AXS SMART CCD, φ/ω
$2\theta_{\text{max}}$:	55.84°
$N(hkl)_{\text{measured}}$, $N(hkl)_{\text{unique}}$:	4075, 2078
Criterion for I_{obs} , $N(hkl)_{\text{gt}}$:	$I_{\text{obs}} > 2 \sigma(I_{\text{obs}})$, 2037
$N(\text{param})_{\text{refined}}$:	91
Programs:	SHELXL-97 [6], DIAMOND [7]

Table 2. Atomic coordinates and displacement parameters (in \AA^2).

Atom	Site	x	y	z	U_{11}	U_{22}	U_{33}	U_{12}	U_{13}	U_{23}
Sb	2a	0.81740(3)	0.76783(2)	0.98199(2)	0.0247(1)	0.0193(1)	0.0235(1)	−0.0014(1)	−0.00049(9)	−0.0024(1)
K	2a	0.6955(1)	1.0534(1)	0.50699(9)	0.0300(5)	0.0380(5)	0.0314(5)	−0.0002(4)	−0.0020(4)	−0.0003(4)
P(1)	2a	0.6923(1)	0.3492(1)	0.82655(9)	0.0176(5)	0.0174(4)	0.0167(4)	−0.0019(4)	−0.0007(3)	0.0009(4)
P(2)	2a	0.7957(1)	0.5678(1)	0.69610(9)	0.0191(4)	0.0199(4)	0.0172(4)	−0.0019(4)	−0.0001(3)	0.0016(4)
S(1)	2a	0.6716(1)	0.4642(1)	1.01839(8)	0.0297(5)	0.0219(4)	0.0174(5)	−0.0062(4)	0.0032(4)	−0.0019(4)
S(2)	2a	0.9110(1)	0.1592(1)	0.8275(1)	0.0230(5)	0.0213(4)	0.0247(5)	0.0034(4)	−0.0038(4)	−0.0015(4)
S(3)	2a	0.4285(1)	0.2626(2)	0.74772(8)	0.0194(4)	0.0263(4)	0.0233(4)	−0.0057(5)	−0.0035(3)	0.0011(5)
S(4)	2a	1.0547(1)	0.6438(1)	0.8062(1)	0.0180(4)	0.0297(4)	0.0232(5)	−0.0036(4)	0.0002(4)	−0.0025(4)
S(5)	2a	0.5878(1)	0.7546(2)	0.73068(9)	0.0251(4)	0.0226(4)	0.0268(4)	0.0045(5)	−0.0041(3)	−0.0007(5)
S(6)	2a	0.8271(2)	0.4844(2)	0.5078(1)	0.0308(6)	0.0367(6)	0.0184(5)	−0.0037(5)	0.0023(4)	−0.0030(4)

* Correspondence author (e-mail: vmanriqu@uchile.cl)

Acknowledgments. This work was supported by FONDECYT through operating grants No. 1020683 and "Beca Apoyo Tesis CONICYT 2002" and by the Fundación Andes with a single crystal diffractometer.

References

1. Ruiz-León, D.; Manríquez, V.; Kasaneva, J.; Avila, R. E.: Insertion of trivalent cations in layered MPS₃ (M = Mn, Cd) materials. *Mater. Res. Bull.* **37** (2002) 981-989.
2. Galdámez, A.; Manríquez, V.; Kasaneva, J.; Avila, R. E.: Synthesis, characterization and electrical properties of quaternary selenodiphosphates: AMP₂Se₆ with A = Cu, Ag and M = Bi, Sb. *Mater. Res. Bull.* **38** (2003) 1063-1072.
3. Manríquez, V.; Galdámez, A.; Ruiz León, D.; Garland, M. T.; Jiménez, M.: Crystal structure of Potassium Bismuth hexathiodiphosphate KBiP₂S₆. *Z. Kristallogr. NCS* **218** (2003) 151-152.
4. McCarthy, T.; Kanatzidis, M.: Synthesis in molten alkali metal polythiophosphate fluxes. The new quaternary bismuth and antimony thiophosphates ABiP₂S₇ (A = K, Rb), A₃M(PS₄)₂ (A = K, Rb, Cs; M = Sb, Bi), Cs₃Bi₂(PS₄) and Na_{0.16}Bi_{1.28}P₂S₆. *J. Alloys Compds.* **236** (1996) 70-85.
5. Breshears, J.; Kanatzidis, M.: β -KBiP₂Se₆ (M = Sb, Bi): Kinetically Accessible Phases Obtained from rapid crystallization of amorphous precursors. *J. Am. Chem. Soc.* **122** (2000) 7839-7840.
6. Sheldrick, G. M.: SHELXL-97. Program for crystal structure refinement. University of Göttingen, Germany 1997.
7. Brandenburg, K.: Diamond Version 2.1b, Crystal Impact GbR, Copyright 1996-1999.