

Two New Stilbene Carbamates

EDUARDO A. SOTO BUSTAMANTE, THOMAS HANEMANN
AND WOLFGANG HAASE

*Institut für Physikalische Chemie, Technische
Hochschule Darmstadt, Petersenstrasse 20,
64287 Darmstadt, Germany*

INGRID SVOBODA AND HARTMUT FUESS

*Strukturforschung, FB Materialwissenschaft,
Technische Hochschule Darmstadt, Petersenstrasse 20,
64287 Darmstadt, Germany*

(Received 7 November 1994; accepted 5 April 1995)


Abstract

The syntheses and solid-state structures of two stilbene carbamates, 4-[2-(4-nitrophenyl)ethenyl]phenylcarbamic acid ethyl ester, $C_{17}H_{16}N_2O_4$, (1), and 4-[2-(2,4-dinitrophenyl)ethenyl]phenylcarbamic acid ethyl ester, $C_{17}H_{15}N_3O_6$, (2), are described. The crystallization from tetrahydrofuran solutions occurs in the monoclinic system with space group $P2_1/n$. Both molecules display hydrogen bonding. For compound (2), there are two different molecules in the asymmetric unit.

Comment

Nonlinear optical properties of inorganic crystals are well known and devices are commercially available. Organic crystals promise to be useful in a broader range of applications. Second harmonic efficiencies of alkyl esters of nitrophenylcarbamic acids have been investigated previously (Francis & Tiers, 1992). These compounds had been found to crystallize with non-centrosymmetric structures. The strength of the nonlinear optical properties of these systems depended on the solvent of crystallization. Therefore, our first task in the search for non-centrosymmetric structures was to synthesize molecules of the same type with large conjugated systems,

with a view to improving the nonlinear optical properties. The two different carbamate dyes prepared, (1) and (2), possess an enhanced π system *via* a stilbene core, which is present in many dyes that exhibit strong nonlinear optical properties. However, neither structure presented here is non-centrosymmetric.

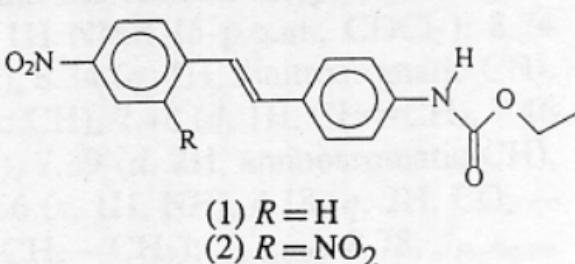

(1) $R = \text{H}$
(2) $R = \text{NO}_2$

Both compounds display hydrogen bonding (Tables 2 and 4). For compound (1), hydrogen bonds are formed between the NH of the carbamate group and the nitro group in an adjacent molecule (Fig. 3a). For compound (2), a second molecule is present in the asymmetric unit with its amino group H atom bonded to the carbonyl group of the first molecule (Fig. 3b). As can be seen in Fig. 3(b), the difference between the two molecules in compound (2) is that the second molecule is 'hanging' by one hydrogen bond from a zigzag net created for the first molecule *via* two hydrogen bonds. Also, the planarity of the second molecule is slightly distorted (by *ca* 10°), probably as a result of steric hindrance between the lateral nitro groups in both molecules. This is evidenced by the torsion angles C2—C3—C7—C8 [$-167.0(3)^\circ$] and C19—C20—C24—C25 [$-180.0(3)^\circ$]

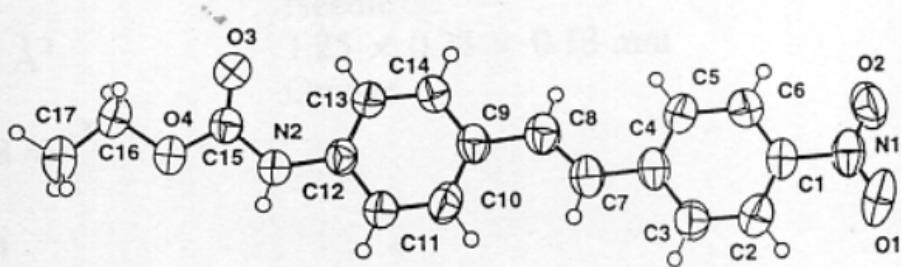


Fig. 1. Displacement ellipsoid plot of (1) at the 50% probability level.

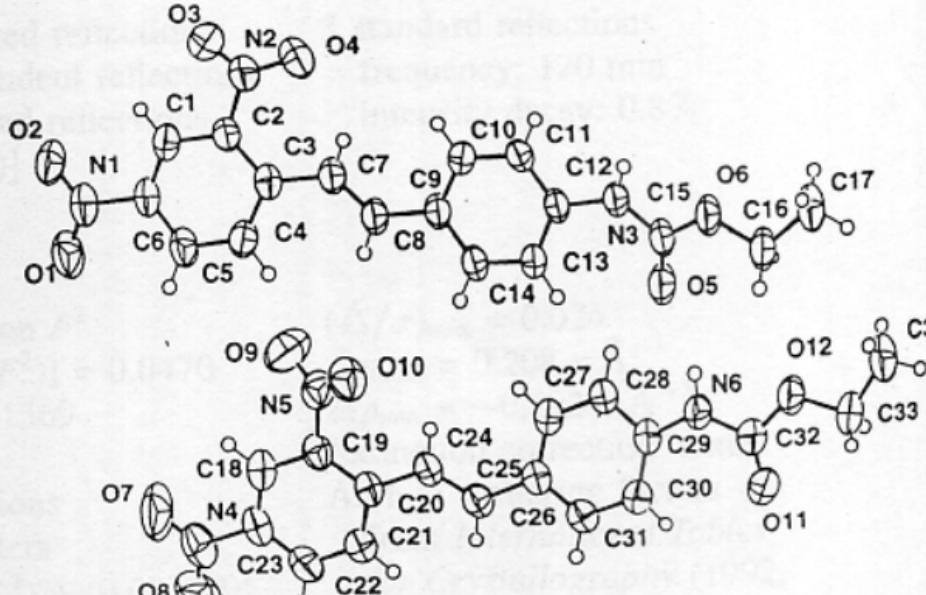


Fig. 2. Displacement ellipsoid plot of (2) at the 50% probability level.

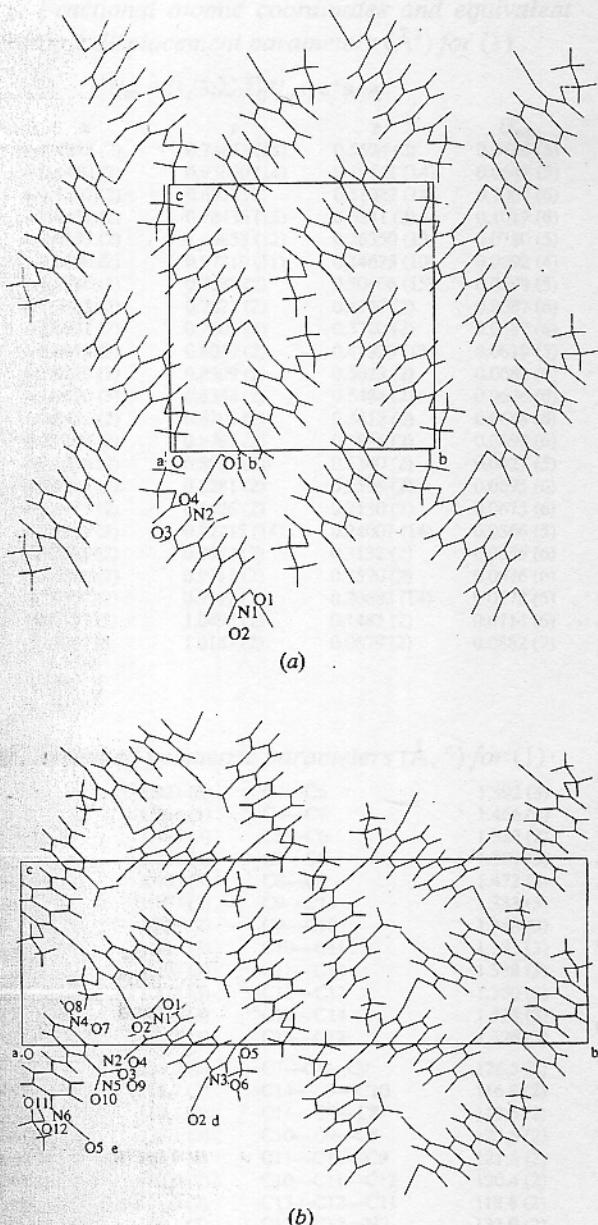


Fig. 3. Projection on the bc plane showing the hydrogen-bonding scheme for (a) compound (1) and (b) compound (2).

Experimental

Compound (1): 10.0 g (42 mmol) of 4'-amino-4-nitrostilbene and 8.0 g (58.6 mmol) of ethyl chloroformate were dissolved in 120 ml of dry toluene and refluxed for 24 h. After cooling to room temperature, the solvent was evaporated *in vacuo* and the residue recrystallized twice from acetone; yield 75%, m.p. 483.9 K. The compound shows solid polymorphism as well as a monotropic liquid crystalline phase: C1 440.0, C2 483.9 K I; cooling: C 461.0 N 467.0 K I. ^1H NMR (δ p.p.m., CDCl_3): 8.21 (*d*, 2H, nitroaromatic CH), 7.61 (*d*, 2H, nitroaromatic CH), 7.51 (*d*, 2H, aminoaromatic CH), 7.43 (*d*, 2H, aminoaromatic CH), 7.22 (*d*, 1H, $\text{CH}=\text{CH}$), 7.05 (*d*, 1H, $\text{CH}=\text{CH}$), 6.69 (*s*, 1H, NH), 4.24 (*c*, 2H, CH_2), 1.33 (*t*, 3H, CH_3). MS (70 eV) m/z : 312 (M^+ , 100%), 313 ($M+1$), 314

($M+2$). Elemental analysis: calculated C 65.26, H 5.13, N 9.00%; found C 65.38, H 5.13, N 8.97%.

Compound (2): 11.2 g (39.3 mmol) of 4'-amino-2,4-dinitrostilbene and 6.5 g of ethyl chloroformate (60 mmol) were refluxed in 300 ml of dry toluene for 24 h under an argon atmosphere. After cooling to room temperature, the solvent was evaporated *in vacuo* and the residue recrystallized twice from acetone; yield 63%. ^1H NMR (δ p.p.m., CDCl_3): 8.74 (*d*, 1H, dinitroaromatic CH), 8.34 (*q*, 1H, dinitroaromatic CH), 7.90 (*d*, 1H, dinitroaromatic CH), 7.48 (*d*, 1H, $\text{CH}=\text{CH}$), 7.46 (*d*, 2H, aminoaromatic CH), 7.39 (*d*, 2H, aminoaromatic CH), 7.18 (*d*, 1H, $\text{CH}=\text{CH}$), 6.66 (*s*, 1H, NH), 4.18 (*q*, 2H, CO_2-CH_2), 1.29 (*t*, 3H, $\text{CO}_2-\text{CH}_2-\text{CH}_3$); $J_{o\text{-dinitro}}$ 8.78, $J_{m\text{-dinitro}}$ 2.28, $J_{o\text{-amino}}$ 8.6, $J_{\text{CH}=\text{CH}}$ 16.2 Hz. MS (70 eV) m/z : 357 (M^+ , 100%), 358 ($M+1$), 359 ($M+2$). Elemental analysis: calculated C 57.14, H 4.20 N 11.77%; found C 56.89, H 4.18, N 11.92%.

DSC measurements (Dupont Thermal Analyzer 990) and polarizing microscopy (Leitz Orthoplan Pol), supported with a Hotstation (Mettler FP 800), were used to characterize the thermodynamic properties.

Good quality crystals of both compounds were obtained after a week, by slow evaporation from concentrated solutions (~1g per 20 ml) in tetrahydrofuran at 308 K.

Compound (1)

Crystal data

$C_{17}\text{H}_{16}\text{N}_2\text{O}_4$
 $M_r = 312.35$
Monoclinic
 $P2_1/n$
 $a = 8.544$ (3) Å
 $b = 13.193$ (1) Å
 $c = 13.616$ (1) Å
 $\beta = 90.23$ (2) $^\circ$
 $V = 1534.8$ (6) Å 3
 $Z = 4$
 $D_x = 1.352 \text{ Mg m}^{-3}$

Mo $K\alpha$ radiation
 $\lambda = 0.71069$ Å
Cell parameters from 25 reflections
 $\theta = 3.08\text{--}17.08^\circ$
 $\mu = 0.059 \text{ mm}^{-1}$
 $T = 297$ (2) K
Needle
 $1.25 \times 0.23 \times 0.18$ mm
Orange

Data collection

Enraf–Nonius CAD-4 diffractometer
 $w/2\theta$ scans
Absorption correction:
none
5411 measured reflections
2123 independent reflections
1784 observed reflections
[$I > 2\sigma(I)$]

$R_{\text{int}} = 0.0209$
 $\theta_{\text{max}} = 22.97^\circ$
 $h = -9 \rightarrow 9$
 $k = -14 \rightarrow 14$
 $l = -14 \rightarrow 14$
3 standard reflections
frequency: 120 min
intensity decay: 0.8%

Refinement

Refinement on F^2
 $R[F^2 > 2\sigma(F^2)] = 0.0470$
 $wR(F^2) = 0.1369$
 $S = 1.116$
2123 reflections
218 parameters
 $w = 1/(\sigma^2(F_o^2) + (0.0819P)^2 + 0.2339P)$
where $P = (F_o^2 + 2F_c^2)/3$

$(\Delta/\sigma)_{\text{max}} = 0.024$
 $\Delta\rho_{\text{max}} = 0.208 \text{ e } \text{\AA}^{-3}$
 $\Delta\rho_{\text{min}} = -0.192 \text{ e } \text{\AA}^{-3}$
Extinction correction: none
Atomic scattering factors
from International Tables
for Crystallography (1992,
Vol. C, Tables 4.2.6.8 and
6.1.1.4)

Table 1. Fractional atomic coordinates and equivalent isotropic displacement parameters (Å²) for (1)

	<i>x</i>	<i>y</i>	<i>z</i>	<i>U</i> _{eq}	Compound (2)	Crystal data	Mo Kα radiation
				$U_{eq} = (1/3)\sum_i \sum_j U_{ij} a_i^* a_j^* \mathbf{a}_i \cdot \mathbf{a}_j$	C ₁₇ H ₁₅ N ₃ O ₆	$M_r = 714.64$	$\lambda = 0.71069 \text{ Å}$
N1	-1.4242 (2)	0.74871 (15)	0.5524 (2)	0.0740 (5)	Monoclinic	<i>P</i> 2 ₁ / <i>n</i>	Cell parameters from 25 reflections
N2	-0.1460 (2)	0.93050 (14)	0.19141 (14)	0.0647 (5)		<i>a</i> = 8.607 (2) Å	$\theta = 2.99\text{--}16.53^\circ$
O1	-1.5207 (2)	0.6959 (2)	0.51022 (14)	0.1007 (6)		<i>b</i> = 33.918 (8) Å	$\mu = 0.110 \text{ mm}^{-1}$
O2	-1.4452 (2)	0.78436 (15)	0.6341 (2)	0.1017 (6)		<i>c</i> = 11.430 (2) Å	<i>T</i> = 301 (2) K
O3	-0.0337 (2)	1.06853 (12)	0.26350 (12)	0.0780 (5)		$\beta = 90.54 (2)^\circ$	Needle
O4	0.0890 (2)	0.97819 (11)	0.14675 (10)	0.0692 (4)		<i>V</i> = 3337 (1) Å ³	1.25 × 0.15 × 0.15 mm
C1	-1.2746 (2)	0.7688 (2)	0.50406 (15)	0.0588 (5)		<i>Z</i> = 4	Orange
C2	-1.2433 (2)	0.7222 (2)	0.4167 (2)	0.0687 (6)		$D_x = 1.423 \text{ Mg m}^{-3}$	
C3	-1.1021 (2)	0.7405 (2)	0.3720 (2)	0.0687 (6)			
C4	-0.9918 (2)	0.8047 (2)	0.41323 (15)	0.0618 (5)			
C5	-1.0279 (2)	0.8509 (2)	0.5023 (2)	0.0682 (6)			
C6	-1.1690 (3)	0.8334 (2)	0.5484 (2)	0.0676 (6)			
C7	-0.8437 (2)	0.8201 (2)	0.3612 (2)	0.0688 (6)			
C8	-0.7280 (2)	0.8797 (2)	0.3865 (2)	0.0699 (6)			
C9	-0.5788 (2)	0.8923 (2)	0.3340 (2)	0.0627 (5)			
C10	-0.5291 (2)	0.8281 (2)	0.2595 (2)	0.0695 (6)			
C11	-0.3873 (2)	0.8426 (2)	0.2130 (2)	0.0675 (6)			
C12	-0.2901 (2)	0.92217 (14)	0.24007 (14)	0.0566 (5)			
C13	-0.3386 (2)	0.9873 (2)	0.3132 (2)	0.0655 (6)			
C14	-0.4800 (2)	0.9712 (2)	0.3590 (2)	0.0676 (6)			
C15	-0.0307 (2)	0.9992 (2)	0.20683 (14)	0.0578 (5)			
C16	0.2173 (2)	1.0495 (2)	0.1483 (2)	0.0714 (6)			
C17	0.3262 (3)	1.0187 (2)	0.0679 (2)	0.0882 (7)			

Data collection

Enraf–Nonius CAD-4
diffractometer
 $\omega/2\theta$ scans
Absorption correction:
none
4872 measured reflections
4608 independent reflections
3260 observed reflections
 $[I > 2\sigma(I)]$

$R_{int} = 0.060$
 $\theta_{max} = 22.98^\circ$
 $h = -9 \rightarrow 9$
 $k = 0 \rightarrow 37$
 $l = 0 \rightarrow 12$
3 standard reflections
frequency: 120 min
intensity decay: 0.2%

Table 2. Selected geometric parameters (Å, °) for (1)

N1—O1	1.221 (3)	C4—C5	1.392 (3)
N1—O2	1.221 (3)	C4—C7	1.466 (3)
N1—C1	1.465 (3)	C5—C6	1.382 (3)
N2—C15	1.354 (3)	C7—C8	1.309 (3)
N2—C12	1.405 (3)	C8—C9	1.473 (3)
O3—C15	1.197 (2)	C9—C14	1.383 (3)
O4—C15	1.341 (2)	C9—C10	1.388 (3)
O4—C16	1.445 (3)	C10—C11	1.383 (3)
C1—C2	1.367 (3)	C11—C12	1.388 (3)
C1—C6	1.378 (3)	C12—C13	1.380 (3)
C2—C3	1.375 (3)	C13—C14	1.378 (3)
C3—C4	1.385 (3)	C16—C17	1.496 (3)
O1—N1—O2	123.2 (2)	C7—C8—C9	126.5 (2)
O1—N1—C1	118.7 (2)	C14—C9—C10	116.8 (2)
O2—N1—C1	118.1 (2)	C14—C9—C8	119.6 (2)
C15—N2—C12	128.1 (2)	C10—C9—C8	123.6 (2)
C15—O4—C16	115.9 (2)	C11—C10—C9	121.5 (2)
C2—C1—C6	122.0 (2)	C10—C11—C12	120.4 (2)
C2—C1—N1	119.0 (2)	C13—C12—C11	118.8 (2)
C6—C1—N1	119.1 (2)	C13—C12—N2	123.9 (2)
C1—C2—C3	118.8 (2)	C11—C12—N2	117.3 (2)
C2—C3—C4	121.7 (2)	C14—C13—C12	119.8 (2)
C3—C4—C5	117.9 (2)	C13—C14—C9	122.7 (2)
C3—C4—C7	118.4 (2)	O3—C15—O4	124.7 (2)
C5—C4—C7	123.7 (2)	O3—C15—N2	126.5 (2)
C6—C5—C4	121.3 (2)	O4—C15—N2	108.9 (2)
C1—C6—C5	118.4 (2)	O4—C16—C17	106.7 (2)
C8—C7—C4	127.4 (2)		
O1—N1—C1—C2	-4.6 (3)	C10—C11—C12—N2	178.3 (2)
O2—N1—C1—C2	174.2 (2)	C15—N2—C12—C13	1.3 (3)
O1—N1—C1—C6	176.0 (2)	C15—N2—C12—C11	-177.9 (2)
O2—N1—C1—C6	-5.2 (3)	N2—C12—C13—C14	-177.9 (2)
N1—C1—C2—C3	-179.3 (2)	C16—O4—C15—O3	-3.9 (3)
C3—C4—C7—C8	177.7 (2)	C16—O4—C15—N2	175.2 (2)
C5—C4—C7—C8	-2.5 (3)	C12—N2—C15—O3	-2.9 (3)
C4—C7—C8—C9	178.7 (2)	C12—N2—C15—O4	178.0 (2)
C7—C8—C9—C14	168.1 (2)	C15—O4—C16—C17	-173.1 (2)
C7—C8—C9—C10	-12.4 (3)		

$$D—H \cdots A \quad D—H \quad H \cdots A \quad D \cdots A \quad D—H \cdots A$$

$$N2—HN2 \cdots O1^i \quad 0.82 (2) \quad 2.38 (2) \quad 3.168 (3) \quad 162 (2)$$

Symmetry code: (i) $\frac{1}{2} + x, \frac{3}{2} + y, z - \frac{1}{2}$.

Refinement

Refinement on F^2
 $R[F^2 > 2\sigma(F^2)] = 0.0435$
 $wR(F^2) = 0.2022$
 $S = 1.044$
4566 reflections
478 parameters
 $w = 1/[\sigma^2(F_o^2) + (0.0680P)^2 + 1.5520P]$
where $P = (F_o^2 + 2F_c^2)/3$
 $(\Delta/\sigma)_{max} = 0.077$
 $\Delta\rho_{max} = 0.255 \text{ e } \text{\AA}^{-3}$
 $\Delta\rho_{min} = -0.212 \text{ e } \text{\AA}^{-3}$

Extinction correction:
SHELXL93 (Sheldrick, 1993)
Extinction coefficient:
0.0039 (6)
Atomic scattering factors
from International Tables
for Crystallography (1992,
Vol. C, Tables 4.2.6.8 and
6.1.1.4)

Table 3. Fractional atomic coordinates and equivalent isotropic displacement parameters (Å²) for (2)

	<i>x</i>	<i>y</i>	<i>z</i>	<i>U</i> _{eq}
C1	0.3817 (3)	0.28776 (9)	0.5676 (3)	0.0603 (8)
C2	0.2328 (3)	0.27978 (9)	0.5274 (3)	0.0559 (7)
C3	0.1523 (3)	0.24543 (9)	0.5571 (2)	0.0525 (7)
C4	0.2334 (3)	0.21920 (9)	0.6300 (2)	0.0602 (8)
C5	0.3802 (3)	0.22704 (10)	0.6731 (2)	0.0607 (8)
C6	0.4518 (3)	0.26114 (9)	0.6404 (2)	0.0546 (7)
C7	-0.0019 (3)	0.23541 (9)	0.5121 (3)	0.0594 (8)
C8	-0.0930 (3)	0.20771 (9)	0.5521 (3)	0.0595 (8)
C9	-0.2457 (3)	0.19707 (9)	0.5045 (2)	0.0542 (7)
C10	-0.3224 (3)	0.21935 (9)	0.4197 (2)	0.0584 (8)
C11	-0.4635 (3)	0.20780 (9)	0.3746 (2)	0.0570 (7)
C12	-0.5336 (3)	0.17350 (9)	0.4132 (2)	0.0519 (7)
C13	-0.4601 (3)	0.15088 (9)	0.4973 (3)	0.0596 (8)
C14	-0.3191 (3)	0.16316 (9)	0.5432 (3)	0.0609 (8)
C15	-0.7840 (3)	0.13769 (9)	0.4041 (3)	0.0570 (7)
C16	-1.0305 (3)	0.10992 (11)	0.3596 (3)	0.0711 (9)
C17	-1.1600 (3)	0.11836 (12)	0.2745 (3)	0.0820 (11)
O1	0.6647 (3)	0.24904 (8)	0.7587 (2)	0.0854 (7)
O2	0.6769 (3)	0.29864 (8)	0.6426 (2)	0.0827 (7)
O3	0.2536 (3)	0.32827 (9)	0.3872 (3)	0.1207 (12)
O4	0.0256 (3)	0.31420 (8)	0.4461 (3)	0.1055 (9)

-0.7760 (2)	0.11973 (7)	0.4940 (2)	0.0772 (7)	C11—C10—C9	121.3 (3)	C28—C27—C26	121.5 (3)	
-0.9043 (2)	0.13617 (7)	0.3290 (2)	0.0682 (6)	C10—C11—C12	120.4 (3)	C27—C28—C29	120.7 (3)	
0.6092 (3)	0.27033 (9)	0.6835 (2)	0.0652 (7)	C13—C12—C11	119.4 (2)	C30—C29—C28	118.9 (3)	
0.1652 (3)	0.30978 (9)	0.4492 (3)	0.0805 (8)	C13—C12—N3	123.2 (3)	C30—C29—N6	124.1 (3)	
-0.6775 (3)	0.16310 (8)	0.3616 (2)	0.0600 (7)	C11—C12—N3	117.4 (2)	C28—C29—N6	117.0 (3)	
1.2437 (3)	0.11524 (10)	1.0073 (3)	0.0629 (8)	C12—C13—C14	119.5 (3)	C31—C30—C29	119.4 (3)	
1.1078 (3)	0.11178 (9)	0.9427 (2)	0.0555 (7)	C13—C14—C9	122.0 (3)	C30—C31—C26	122.8 (3)	
0.9964 (3)	0.08247 (9)	0.9636 (2)	0.0541 (7)	O5—C15—O6	124.7 (3)	O11—C32—O12	124.7 (3)	
1.0334 (3)	0.05609 (10)	1.0533 (3)	0.0649 (8)	O5—C15—N3	126.9 (3)	O11—C32—N6	126.6 (3)	
1.1681 (4)	0.05857 (10)	1.1174 (3)	0.0680 (9)	O6—C15—N3	108.4 (3)	O12—C32—N6	108.7 (3)	
1.2708 (3)	0.08806 (10)	1.0930 (3)	0.0639 (8)	O6—C16—C17	106.3 (3)	O12—C33—C34	106.5 (3)	
0.8469 (3)	0.08094 (9)	0.9027 (3)	0.0584 (8)	C15—O6—C16	116.4 (2)	C32—O12—C33	116.2 (2)	
0.7361 (3)	0.05468 (9)	0.9168 (3)	0.0607 (8)	O1—N1—O2	123.5 (3)	O8—N4—O7	124.6 (3)	
0.5857 (3)	0.05498 (9)	0.8563 (2)	0.0536 (7)	O1—N1—C6	118.0 (3)	O8—N4—C23	117.8 (4)	
0.5301 (3)	0.08781 (9)	0.7964 (2)	0.0580 (7)	O2—N1—C6	118.4 (3)	O7—N4—C23	117.6 (4)	
0.3919 (3)	0.08672 (9)	0.7351 (2)	0.0561 (7)	O4—N2—O3	123.0 (3)	O10—N5—O9	123.4 (3)	
0.3037 (3)	0.05245 (9)	0.7307 (2)	0.0525 (7)	O4—N2—C2	119.3 (3)	O10—N5—C19	119.4 (3)	
0.3552 (3)	0.01969 (9)	0.7917 (3)	0.0632 (8)	O3—N2—C2	117.6 (3)	O9—N5—C19	117.1 (3)	
0.4939 (3)	0.02154 (10)	0.8531 (3)	0.0643 (8)	C15—N3—C12	127.2 (3)	C32—N6—C29	126.8 (3)	
0.0444 (3)	0.02876 (10)	0.6695 (3)	0.0578 (7)	C6—C1—C2—N2	179.9 (3)	C23—C18—C19—N5	-177.7 (3)	
-0.2074 (3)	0.01802 (10)	0.5912 (3)	0.0720 (9)	N2—C2—C3—C4	178.4 (3)	N5—C19—C20—C21	178.0 (3)	
-0.3134 (4)	0.03785 (13)	0.5061 (4)	0.0953 (12)	N2—C2—C3—C7	1.8 (4)	N5—C19—C20—C24	-6.3 (4)	
1.5082 (4)	0.11666 (13)	1.1329 (3)	0.1402 (14)	C2—C1—C6—N1	-179.4 (3)	C19—C18—C23—N4	-179.7 (3)	
1.4312 (4)	0.07047 (10)	1.2466 (3)	0.1245 (12)	C4—C5—C6—N1	-179.1 (3)	C21—C22—C23—N4	178.8 (3)	
1.1396 (3)	0.17381 (8)	0.8670 (2)	0.1027 (9)	C2—C3—C7—C8	-167.0 (3)	C21—C20—C24—C25	-4.5 (5)	
0.10270 (3)	0.13119 (8)	0.7573 (2)	0.0786 (7)	C3—C7—C8—C9	-178.2 (3)	C20—C24—C25—C26	178.0 (3)	
0.0329 (2)	0.00104 (7)	0.7326 (2)	0.0795 (7)	C7—C8—C9—C14	169.7 (3)	C24—C25—C26—C31	163.1 (3)	
-0.0656 (2)	0.04068 (7)	0.5932 (2)	0.0681 (6)	C7—C8—C9—C10	-9.6 (5)	C24—C25—C26—C27	-14.6 (5)	
1.4153 (4)	0.09172 (12)	1.1625 (3)	0.0887 (9)	C10—C11—C12—N3	-179.0 (3)	C27—C28—C29—N6	-177.0 (3)	
1.0884 (3)	0.14094 (9)	0.8489 (2)	0.0653 (7)	N3—C12—C13—C14	179.8 (3)	N6—C29—C30—C31	177.2 (3)	
0.1680 (3)	0.05332 (8)	0.6615 (2)	0.0615 (7)	O5—C15—O6—C16	-1.5 (5)	O11—C32—O12—C33	1.1 (4)	
				N3—C15—O6—C16	179.4 (3)	N6—C32—O12—C33	-179.2 (2)	
				C17—C16—O6—C15	170.8 (3)	C34—C33—O12—C32	176.9 (3)	
				C1—C6—N1—O1	171.8 (3)	C18—C23—N4—O8	171.9 (3)	
				C5—C6—N1—O1	-8.7 (4)	C22—C23—N4—O8	-6.8 (5)	
				C1—C6—N1—O2	-7.9 (4)	C18—C23—N4—O7	-6.2 (5)	
				C5—C6—N1—O2	171.6 (3)	C22—C23—N4—O7	175.2 (4)	
				C1—C2—N2—O4	-151.3 (3)	C18—C19—N5—O10	143.6 (3)	
				C3—C2—N2—O4	29.6 (5)	C20—C19—N5—O10	-35.9 (4)	
				C1—C2—N2—O3	31.1 (4)	C18—C19—N5—O9	-34.5 (4)	
				C3—C2—N2—O3	-148.0 (3)	C20—C19—N5—O9	146.0 (3)	
				O5—C15—N3—C12	0.8 (5)	O11—C32—N6—C29	-4.1 (5)	
				O6—C15—N3—C12	179.8 (3)	O12—C32—N6—C29	176.2 (3)	
				C13—C12—N3—C15	19.7 (5)	C30—C29—N6—C32	21.6 (5)	
				C11—C12—N3—C15	-161.6 (3)	C28—C29—N6—C32	-159.7 (3)	
				D—H···A	D—H	H···A	D···A	D—H···A
				N3—H3N···O2 ⁱ	0.88 (3)	2.22 (3)	3.076 (3)	166 (3)
				N6—H6N···O5 ⁱⁱ	0.86 (3)	2.17 (3)	2.999 (4)	162 (3)

Symmetry codes: (i) $x - \frac{3}{2}, \frac{1}{2} - y, z - \frac{1}{2}$; (ii) $1 + x, y, z$.

The structures were solved by direct methods. The positional and anisotropic displacement parameters of all non-H atoms were refined by full-matrix least squares on F^2 . All H atoms except those on the amino group were geometrically positioned using idealized C—H bond lengths.

For both compounds, data collection: CAD-4 EXPRESS (Enraf–Nonius, 1993); cell refinement: CAD-4 EXPRESS; data reduction: REDU4 (Stoe & Cie, 1991); program(s) used to solve structures: SHELLXS86 (Sheldrick, 1985); program(s) used to refine structures: SHELLXL93 (Sheldrick, 1993); molecular graphics: PLUTON93 (Spek, 1993); software used to prepare material for publication: SHELLXL93.

EASB thanks German TELEKOM for financial support.

Lists of structure factors, anisotropic displacement parameters, H-atom coordinates and complete geometry have been deposited with the IUCr (Reference: JZ1028). Copies may be obtained through The Managing Editor, International Union of Crystallography, 5 Abbey Square, Chester CH1 2HU, England.

References

- Enraf–Nonius (1993). *CAD-4 EXPRESS*. Release 5.1. Enraf–Nonius, Delft, The Netherlands.
- Francis, C. V. & Tiers, V. D. (1992). *Chem. Mater.* p. 353.
- Sheldrick, G. M. (1985). *SHELX86. Program for the Solution of Crystal Structures*. Univ. of Göttingen, Germany.
- Sheldrick, G. M. (1993). *SHELXL93. Program for the Refinement of Crystal Structures*. Univ. of Göttingen, Germany.
- Spek, A. L. (1993). *PLUTON93. Program for the Display and Analysis of Crystal and Molecular Structures*. Univ. of Utrecht, The Netherlands.
- Stoe & Cie (1991). *REDU4. Data Reduction Program*. Release 7.08. Stoe & Cie, Darmstadt, Germany.